

11-1-2004

# As-Doped p-Type ZnO Produced by an Evaporation/Sputtering Process

David C. Look

Wright State University - Main Campus, david.look@wright.edu

G. M. Renlund

R. H. Burgener

J. R. Sizelove

Follow this and additional works at: <http://corescholar.libraries.wright.edu/physics>



Part of the [Physics Commons](#)

---

## Repository Citation

Look, D. C., Renlund, G. M., Burgener, R. H., & Sizelove, J. R. (2004). As-Doped p-Type ZnO Produced by an Evaporation/Sputtering Process. *Applied Physics Letters*, 85 (22), 5269-5271.  
<http://corescholar.libraries.wright.edu/physics/89>

This Article is brought to you for free and open access by the Physics at CORE Scholar. It has been accepted for inclusion in Physics Faculty Publications by an authorized administrator of CORE Scholar. For more information, please contact [corescholar@www.libraries.wright.edu](mailto:corescholar@www.libraries.wright.edu).

# As-doped *p*-type ZnO produced by an evaporation/sputtering process

D. C. Look<sup>a)</sup>

Materials and Manufacturing Directorate, Air Force Research Laboratory, Wright-Patterson Air Force Base, Ohio 45433 and Semiconductor Research Center, Wright State University, Dayton, Ohio 45435

G. M. Renlund and R. H. Burgener II

ON International, Inc., 418 West Winchester Street, Salt Lake City, Utah 84107

J. R. Szelove

Materials and Manufacturing Directorate, Air Force Research Laboratory, Wright-Patterson Air Force Base, Ohio 45433

(Received 21 July 2004; accepted 23 September 2004)

Strongly *p*-type ZnO is produced by the following sequence of steps: (1) evaporation of Zn<sub>3</sub>As<sub>2</sub> on a fused-quartz substrate at 350 °C; and (2) sputtering of ZnO with substrate held at 450 °C. The electrical characteristics include: resistivity of 0.4 Ω cm, a mobility of 4 cm<sup>2</sup>/V s, and a hole concentration of about 4 × 10<sup>18</sup> cm<sup>-3</sup>. This resistivity is among the best (lowest) ever reported for *p*-type ZnO. Secondary-ion mass spectroscopic analysis gives an average As concentration about 5 × 10<sup>19</sup> cm<sup>-3</sup>, and a simple one-band fit of the temperature-dependent mobility curve yields an acceptor concentration of about 9 × 10<sup>19</sup> cm<sup>-3</sup>. This is strong evidence that the *p*-type dopant involves As, although it is not clear whether the acceptor is simply As<sub>O</sub> or the recently suggested As<sub>Zn</sub> - 2V<sub>Zn</sub>. © 2004 American Institute of Physics. [DOI: 10.1063/1.1825615]

Crystalline ZnO has been studied for more than 50 years,<sup>1-3</sup> and bulk or epitaxial samples ranging from highly conducting to semi-insulating are now commercially available.<sup>4,5</sup> However, the conduction properties are not easily controlled, and virtually all “undoped” ZnO materials are *n*-type, evidently due to background donor impurities such as Al and H, and native defects such as the Zn interstitial.<sup>1,6-9</sup> Indeed, the production of *p*-type ZnO has proven to be very difficult, and has hindered the development of ZnO-based blue/UV *p*-*n* junction light-emitting diodes (LEDs) and laser diodes (LDs). In the last few years, research on *p*-type ZnO has proceeded at a more rapid pace,<sup>10-30</sup> in spite of the fact that GaN-based blue LEDs and LDs have already been developed and have found many applications. The reason is that ZnO has some fundamental advantages over GaN as a room-temperature emitter, including a more stable exciton, the availability of large-area substrates, the amenability to wet chemical etching, a high radiation resistance, and relatively low materials costs.<sup>3</sup>

A perusal of the periodic table suggests that possible acceptor candidates for ZnO include Group I elements Li, Na, K, Cu, Ag, and Au, substituting for Zn, and Group V elements N, P, As, and Sb, substituting for O. Although most of these elements have been tested as dopants, only N, P, and As, have produced low-resistivity (<100 Ω cm), *p*-type material, to our knowledge. Several groups have found success with N doping,<sup>10,11,13,14,16,18-20,22-25,28,29</sup> which is not surprising since the ionic radius of N is about that of O, so that N should be quite soluble as N<sub>O</sub>. On the other hand, there are only a few reports of *p*-type ZnO from P<sup>21,27,30</sup> or As<sup>12,26</sup> doping, and almost no reports involving any of the other possible dopants. In this letter, we discuss an evaporation/sputtering method of creating As-doped, *p*-type ZnO. This technique has produced *p*-type samples with resistivities as low as 0.1 Ω cm, lower than any others reported so far.

Growth was accomplished by first evaporating a layer of Zn<sub>3</sub>As<sub>2</sub> on a glass substrate at 350 °C, then sputtering ZnO on top of the Zn<sub>3</sub>As<sub>2</sub> at 450 °C. Secondary-ion mass spectroscopic (SIMS) data<sup>31</sup> for layer 12 503 are presented in Fig. 1. The As concentration is accurately determined by comparison with an ion-implanted standard, while the Zn and O concentrations are simply normalized at the surface to their atomic values of about 4 × 10<sup>22</sup> cm<sup>-3</sup>. An important observation from the Zn and O profiles is that they are quite flat over most of the sample, which strongly suggests that the layer is basically ZnO. Further evidence comes from x-ray rocking curves (not shown), which show a dominant (0002) ZnO reflection.

Note in Fig. 1 that the As signal is very strong in the bottom 0.1 μm of the layer, and then quickly reduces to the mid-10<sup>19</sup> cm<sup>-3</sup> range. We interpret the lower part of the SIMS As profile as possibly representing some remaining Zn<sub>3</sub>As<sub>2</sub>, or some As metal, if all of the Zn has reacted to form ZnO. Experiments were performed to test the possible electrical activity of this As-dominated layer, especially since

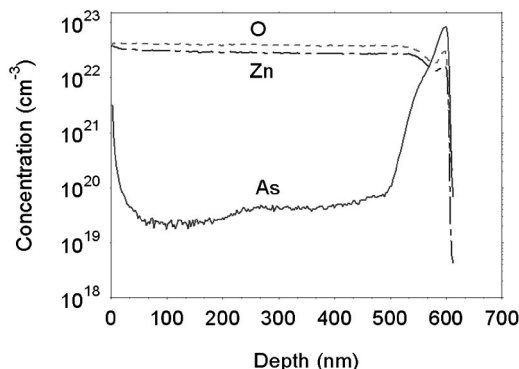


FIG. 1. SIMS measurements of O, Zn, and As in As-doped *p*-type ZnO. The As concentration is determined from an ion-implanted standard, while the O and Zn concentrations are normalized at the surface to roughly their atomic concentrations of 4 × 10<sup>22</sup> cm<sup>-3</sup>.

<sup>a)</sup>Electronic mail: david.look@wpafb.af.mil

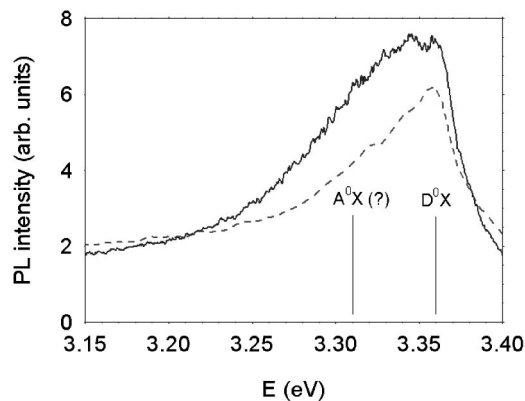


FIG. 2. PL (at 4 K) in two As-doped *p*-type ZnO samples. The dashed line is from a clear region while the solid line represents a darker region, evidently more heavily doped.

both pure  $\text{Zn}_3\text{As}_2$  and As metal are known to be *p*-type, in single-crystalline form. In one such test, the sputtered ZnO was constrained to only partially overlap the evaporated  $\text{Zn}_3\text{As}_2$ , so that three different regions (ZnO,  $\text{Zn}_3\text{As}_2$ , and ZnO/ $\text{Zn}_3\text{As}_2$ ) could be examined separately, after the annealing step was completed. The pure ZnO region turned out to be *n*-type, as expected, while the ZnO/ $\text{Zn}_3\text{As}_2$  was *p*-type, and the  $\text{Zn}_3\text{As}_2$ , semi-insulating. Thus, it is doubtful that the  $\text{Zn}_3\text{As}_2$  could account for the *p*-type conductivity, in this case. Another possibility is that the layer under the ZnO, after all of the processing, is As metal. However, the resistivity of a metal is known to *increase* with temperature, and that of our sample decreases. Thus, we believe that the lower As-rich layer, whether  $\text{Zn}_3\text{As}_2$  or metallic As, is not responsible for the *p*-type activity in our material. The rest of the As profile is reasonably flat at the mid- $10^{19} \text{ cm}^{-3}$  level, which suggests that the main part of the ZnO layer is doped with As by a gas-phase reaction, rather than a diffusion process. However, these issues require further study.

As seen in Fig. 2, 4 K photoluminescence (PL) data show a broad peak in the 3.36 eV region, which is well known as the region of donor-bound exciton ( $D^0X$ ) lines in ZnO. This is further strong evidence that the layer is basically ZnO, and not some undefined mixture of Zn, O, and As. The two PL lines in Fig. 2 are from adjacent areas near the edge of the overlapping ZnO and  $\text{Zn}_3\text{As}_2$  regions, mentioned earlier. The dotted line represents a clear (but still *p*-type) area close to the pure (nonoverlapping) ZnO region, and the solid line, a darker area just inside the overlapping ZnO/ $\text{Zn}_3\text{As}_2$  region. The darker area is presumably more heavily doped with As, and indeed has a stronger *p*-type conductivity. Previous PL studies in N-doped and P-doped *p*-type ZnO have shown that the  $D^0X$  spectrum moves to lower energies in these materials, enhancing the region of the well-known 3.357 eV feature, and that a new line appears in the 3.31 eV region.<sup>19,27,32</sup> Although the identities of these lines are still controversial, there is some evidence that each results from acceptor-bound excitons.<sup>19,33</sup> Whatever its identity, the 3.31 eV line has been found to be associated particularly with *p*-type ZnO, which strengthens the conclusions of the present work.

The temperature-dependent carrier concentration  $p$  and mobility  $\mu_p$  are displayed in Fig. 3. Since the holes are neither fully degenerate nor fully nondegenerate, the curves are not easily amenable to quantitative fitting. However, we have

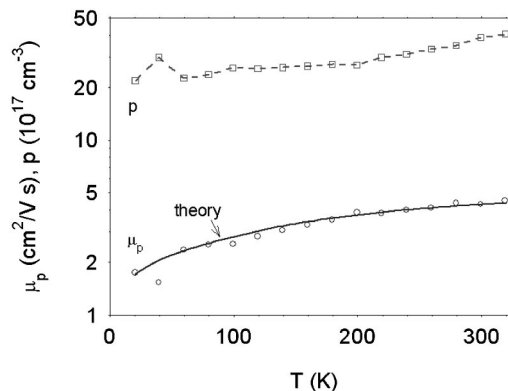


FIG. 3. Hole mobility and concentration in As-doped *p*-type ZnO. The solid curve is a theoretical fit of the mobility assuming a single hole band represented by effective mass  $m^* = 0.64 m_0$ , and a fitting parameter  $N_D = 8 \times 10^{19} \text{ cm}^{-3}$ .

attempted to fit the mobility with a single-band scattering model based on a hole mass of 0.64. (This mass is derived from the assumption that  $N_O$  is a hydrogenic acceptor with a transition energy  $E_{A0} = 133 \text{ meV}$  at low acceptor concentrations. The latter value is estimated from: (1) Hall data,<sup>34</sup> which give  $E_A \sim 90 \text{ meV}$  at  $N_A \sim [N] \sim 10^{19} \text{ cm}^{-3}$ ; and (2) the screening formula,  $E_A = E_{A0} - \beta N_A^{1/3}$ , with  $\beta \sim 2 \times 10^{-5} \text{ meV cm}$ . The mobility fit is surprisingly good, with a fitting parameter  $8 \times 10^{19} \text{ cm}^{-3}$  for the donor concentration  $N_D$ . The acceptor concentration  $N_A$  would then have to be about  $9 \times 10^{19} \text{ cm}^{-3}$ , since the hole concentration at high temperature is in the  $10^{19} \text{ cm}^{-3}$  range. In view of the rather severe approximations involved in the scattering model, it is seen that  $N_A$  is quite consistent with the As concentration of about  $5 \times 10^{19}$ . It is doubtful that the agreement would be this good if the measured layer did not basically consist of As-doped ZnO, as claimed in this work.

Thus, the SIMS, x-ray diffraction, PL, and *T*-dependent Hall-effect measurements all indicate that the evaporation/sputtering method discussed here produces low-resistivity, As-doped, *p*-type ZnO. However, the microscopic structure of the As-related acceptor is not clear at this point. The simplest structure would be  $\text{As}_O$ , but density-functional theory suggests that the large ionic radius of As would preclude a high solubility for  $\text{As}_O$ , and also that the consequent strain relaxation would lead to a deep, not shallow, acceptor.<sup>35</sup> Another possibility, recently presented, is that the structure is much more complex, namely,  $\text{As}_{\text{Zn}}-2V_{\text{Zn}}$ , in which the As substitutes on the Zn site, forming a donor, but that it then induces two Zn-vacancy acceptors.<sup>36</sup> The total defect is then acceptor-like, with a (0/-) transition at 0.15 eV above the valence band. This energy is consistent with our results, but more rigorous confirmation would require analysis of Hall-effect measurements in a nondegenerate sample. The  $\text{As}_{\text{Zn}}-2V_{\text{Zn}}$  defect also presumably has a significantly lower formation energy than that of  $\text{As}_O$ , thus predicting a much higher solubility. At this stage, we cannot positively identify either of these structures in our material.

In summary, we have used an evaporation/sputtering method to produce As-doped, *p*-type ZnO. Structural, optical, and electrical properties are all consistent with this conclusion, and the resistivity, an important figure of merit, is among the lowest ever reported for *p*-type ZnO. The dominant acceptor is related to As, but its microscopic structure is not yet established.

The authors wish to thank T. A. Cooper, J. E. Hoelscher, and W. Rice for technical contributions, and D. C. Reynolds and C. W. Litton for helpful discussions. The work of one of the authors (D.C.L.) was supported under US Air Force Contract F33615-00-C-5402, monitored by J. L. Brown.

- <sup>1</sup>D. G. Thomas, *J. Phys. Chem. Solids* **3**, 229 (1957).
- <sup>2</sup>P. Wagner and R. Helbig, *J. Phys. Chem. Solids* **35**, 327 (1974).
- <sup>3</sup>D. C. Look, *Mater. Sci. Eng., B* **80**, 383 (2001).
- <sup>4</sup>ZN Technology, 910 Columbia St., Brea, CA 92821.
- <sup>5</sup>Cermet Inc., 1019 Collier Road, Suite C1, Atlanta, GA 30318.
- <sup>6</sup>H. Shibata, M. Watanabe, M. Sakai, K. Oka, P. Fons, K. Iwata, A. Yamada, K. Matsubara, K. Sakurai, H. Tampo, K. Nakahara, and S. Niki, *Phys. Status Solidi C* **1**, 872 (2004).
- <sup>7</sup>C. G. Van de Walle, *Phys. Rev. Lett.* **85**, 1012 (2000).
- <sup>8</sup>D. C. Look, J. W. Hemsley, and J. R. Sizelove, *Phys. Rev. Lett.* **82**, 2552 (1999).
- <sup>9</sup>B. K. Meyer, H. Alves, D. M. Hofmann, W. Kriegesies, D. Forster, F. Bertram, J. Christen, A. Hoffmann, M. Straßburg, M. Dworzak, U. Haboeck, and A. V. Rodina, *Phys. Status Solidi B* **241**, 231 (2004).
- <sup>10</sup>K. Minegishi, Y. Koiwai, and K. Kikuchi, *Jpn. J. Appl. Phys., Part 2* **36**, L1453 (1997).
- <sup>11</sup>M. Joseph, H. Tabata, and T. Kawai, *Jpn. J. Appl. Phys., Part 2* **38**, L1205 (1999).
- <sup>12</sup>Y. R. Ryu, S. Zhu, D. C. Look, J. M. Wrobel, H. M. Jeong, and H. W. White, *J. Cryst. Growth* **216**, 330 (2000).
- <sup>13</sup>M. Joseph, H. Tabata, H. Saeki, K. Ueda, and T. Kawai, *Physica B* **302–303**, 140 (2001).
- <sup>14</sup>X-L. Guo, H. Tabata, and T. Kawai, *J. Cryst. Growth* **223**, 135 (2001).
- <sup>15</sup>T. V. Butkhuzi, M. M. Sharvashidze, N. M. Gamkrelidze, Kh. V. Gelovani, T. G. Khulordava, N. P. Kekelidze, and E. E. Kekelidze, *Semicond. Sci. Technol.* **16**, 575 (2001).
- <sup>16</sup>A. B. M. A. Ashrafi, I. Suemune, H. Kumano, and S. Tanaka, *Jpn. J. Appl. Phys., Part 2* **41**, L1281 (2002).
- <sup>17</sup>G. Xiong, J. Wilkinson, B. Mischuck, S. Tuzemen, K. B. Ucer, and R. T. Williams, *Appl. Phys. Lett.* **80**, 1195 (2002).
- <sup>18</sup>X-L. Guo, H. Tabata, and T. Kawai, *Opt. Mater. (Amsterdam, Neth.)* **19**, 229 (2002).
- <sup>19</sup>D. C. Look, D. C. Reynolds, C. W. Litton, R. L. Jones, D. B. Eason, and G. Cantwell, *Appl. Phys. Lett.* **81**, 1830 (2002).
- <sup>20</sup>X. Li, Y. Yan, T. A. Gessert, C. L. Perkins, D. Young, C. DeHart, M. Young, and T. J. Coutts, *J. Vac. Sci. Technol. A* **21**, 1342 (2003).
- <sup>21</sup>K. H. Bang, D-K. Hwang, M-C. Park, Y-D. Ko, I. Yun, and J-M. Myoung, *Appl. Surf. Sci.* **210**, 177 (2003).
- <sup>22</sup>B. S. Li, Y. C. Liu, Z. Z. Zhi, D. Z. Shen, Y. M. Lu, J. Y. Zhang, X. W. Fan, R. X. Mu, and D. O. Henderson, *J. Mater. Res.* **18**, 8 (2003).
- <sup>23</sup>A. V. Singh, R. M. Mehra, A. Wakahara, and A. Yoshida, *J. Appl. Phys.* **93**, 396 (2003).
- <sup>24</sup>J. Huang, Z. Ye, H. Chen, B. Zhao, and L. Wang, *J. Mater. Sci. Lett.* **22**, 249 (2003).
- <sup>25</sup>X. Li, Y. Yan, T. A. Gessert, C. DeHart, C. L. Perkins, D. Young, and T. J. Coutts, *Electrochem. Solid-State Lett.* **6**, C56 (2003).
- <sup>26</sup>Y. R. Ryu, T. S. Lee, and H. W. White, *Appl. Phys. Lett.* **83**, 87 (2003).
- <sup>27</sup>K-K. Kim, H-S. Kim, D-K. Hwang, J-H. Lim, and S-J. Park, *Appl. Phys. Lett.* **83**, 63 (2003).
- <sup>28</sup>J. Lu, Y. Zhang, Z. Ye, L. Wang, B. Zhao, and J. Huang, *Mater. Lett.* **57**, 3311 (2003).
- <sup>29</sup>J. Wang, G. Du, B. Zhao, X. Yang, Y. Zhang, Y. Ma, D. Liu, Y. Chang, H. Wang, H. Yang, and S. Yang, *J. Cryst. Growth* **255**, 293 (2003).
- <sup>30</sup>Y. W. Heo, Y. W. Kwon, Y. Li, S. J. Pearton, and D. P. Norton, *Appl. Phys. Lett.* **84**, 3474 (2004).
- <sup>31</sup>Evans East, 104 Windsor Center, Suite 101, East Windsor, NJ 08520.
- <sup>32</sup>D. C. Look and B. Claffin, *Phys. Status Solidi B* **241**, 624 (2004).
- <sup>33</sup>J. Gutowski, N. Presser, and I. Broser, *Phys. Rev. B* **38**, 9746 (1988).
- <sup>34</sup>D. C. Look, B. Claffin, Ya. I. Alivov, and S. J. Park, *Phys. Status Solidi A* **201**, 2203 (2004).
- <sup>35</sup>C. H. Park, S. B. Zhang, and S. H. Wei, *Phys. Rev. B* **66**, 073202 (2002).
- <sup>36</sup>S. Limpijumnong, S. B. Zhang, S. H. Wei, and C. H. Park, *Phys. Rev. Lett.* **92**, 155504 (2004).